

# A combined theoretical and experimental study of the low temperature properties of BaZrO<sub>3</sub>

A. R. Akbarzadeh<sup>1</sup>, I. Kornev<sup>1</sup>, C. Malibert<sup>2</sup>, L. Bellaiche<sup>1</sup>, and J. M. Kiat<sup>3</sup>

<sup>1</sup>*Physics Department, University of Arkansas, Fayetteville, AR 72701, Arkansas, USA*

<sup>2</sup>*Laboratoire d'Etudes des Milieux Nanométriques,  
Université d'Evry Val d'Essonne, 91000 Evry, France and*

<sup>3</sup>*Laboratoire Léon Brillouin, CE Saclay, 91191 Gif-sur-Yvette Cedex, France*

(Dated: February 2, 2008)

Low temperature properties of BaZrO<sub>3</sub> are revealed by combining experimental techniques (X-ray diffraction, neutron scattering and dielectric measurements) with theoretical first-principles-based methods (total energy and linear response calculations within density functional theory, and effective Hamiltonian approaches incorporating/neglecting zero-point phonon vibrations). Unlike most of the perovskite systems, BaZrO<sub>3</sub> does not undergo any (long-range-order) structural phase transition and thus remains cubic and paraelectric down to 2 K, even when neglecting zero-point phonon vibrations. On the other hand, these latter pure quantum effects lead to a negligible thermal dependency of the cubic lattice parameter below  $\simeq 40$  K. They also affect the dielectricity of BaZrO<sub>3</sub> by inducing an overall saturation of the real part of the dielectric response, for temperatures below  $\simeq 40$  K. Two fine structures in the real part, as well as in the imaginary part, of dielectric response are further observed around 50-65 K and 15 K, respectively. Microscopic origins (e.g., unavoidable defects and oxygen octahedra rotation occurring at a local scale) of such anomalies are suggested. Finally, possible reasons for the facts that some of these dielectric anomalies have not been previously reported in the better studied KTaO<sub>3</sub> and SrTiO<sub>3</sub> incipient ferroelectrics are also discussed.

## I. INTRODUCTION

BaZrO<sub>3</sub> is a ceramic oxide of the perovskite family structure with a large lattice constant, high melting point, small thermal expansion coefficient, low dielectric loss and low thermal conductivity (see, e.g. Refs. 1,2,3,4,5,6,7,8,9,10,11,12,13 and references therein). These afore-mentioned properties make BaZrO<sub>3</sub> (i) a very good candidate to be used as an inert crucible in crystal growth techniques<sup>7,11</sup>, (ii) an excellent material for wireless communications<sup>1,10</sup> and (iii) a very good substrate in thin film deposition<sup>1,3</sup>. BaZrO<sub>3</sub> is also one of the two parent compounds of the (Pb-free and thus environmental-friendly) Ba(Zr,Ti)O<sub>3</sub> solid solutions, which is promising for manufacturing high Q materials with a variety of applications in microwave industry<sup>13</sup>.

Interestingly, properties of BaZrO<sub>3</sub> have been measured as long as 40 years ago, as well as very recently<sup>1,2,3</sup>, but only at room or higher temperature (to the best of our knowledge). Similarly, we are not aware of any calculation (either from phenomenological theory or first-principles calculations) predicting the dielectric properties of BaZrO<sub>3</sub>. As a result, low-temperature dielectric properties of BaZrO<sub>3</sub> have never been investigated, despite the fact that many unusual effects are known to occur in some perovskite materials between 0 and 50 K. One drastic example of such effects is the (temperature-independent) plateau and large values of the real part of the dielectric response in KTaO<sub>3</sub> and SrTiO<sub>3</sub>, which arise from the quantum-induced suppression of ferroelectricity in these materials. Other examples are the anomalous peaks observed around 10-50 K for the imaginary part of the dielectric response in KTaO<sub>3</sub>,

K(Ta,Nb)O<sub>3</sub>, (Pb,Lu)TiO<sub>3</sub>:Cu<sup>14,15</sup>, SrTiO<sub>3</sub><sup>15,16</sup>, that are neither associated with structural phase transition nor do have a corresponding peak in the real part of the dielectric response (which conflicts with the well-established Kramers-Kronig relations<sup>17</sup>).

The aim of this article is to investigate the low-temperature behavior of BaZrO<sub>3</sub> from measurements and first-principles-based simulations. We report several unusual features in the real and imaginary parts of the dielectric responses while *no* long-range ferroelectric, antiferroelectric or antiferrodistortive structural phase transition occurs in BaZrO<sub>3</sub> down to 2 K. Discussions and similarities/differences between BaZrO<sub>3</sub> and the (better-studied) KTaO<sub>3</sub> and SrTiO<sub>3</sub>-related materials are also indicated to better understand the low-temperature dielectric anomalies reported in several perovskites.

This article is organized as follows. Sec. II describes the experimental and theoretical methods we used to investigate BaZrO<sub>3</sub>. Sec. III reports the measurements and predictions for structural and dielectric properties. Finally, Sections IV and V provide a discussion and conclusion, respectively.

## II. METHODOLOGY

### A. EXPERIMENTAL PROCEDURES

Powder samples of BaZrO<sub>3</sub> were synthesized by solid state reaction by calcination at 1400 K and sintering at 1600 K starting from stoichiometric amounts of the corresponding oxides (BaCO<sub>3</sub>, ZrO<sub>2</sub>). The synthesized samples were well crystallized and no presence of parasitic phases was evidenced by X-ray diffraction (XRD) and

TABLE I: The LDA-derived  $H_{\text{eff}}$  parameters in atomic units for  $\text{BaZrO}_3$  following the notation in Ref [29].

|                   |            |         |                      |          |           |         |
|-------------------|------------|---------|----------------------|----------|-----------|---------|
| lattice constant  | $a_0$      | 7.91943 | Soft mode mass       | 75.721   |           |         |
| Onsite            | $\kappa_2$ | 0.0183  | $\alpha$             | 0.009733 | $\gamma$  | 0.01663 |
|                   | $j_1$      | 0.00738 | $j_2$                | 0.02311  |           |         |
| Intersite         | $j_3$      | 0.00262 | $j_4$                | -0.00163 | $j_5$     | 0.00120 |
|                   | $j_6$      | 0.00049 | $j_7$                | 0.00024  |           |         |
| Elastic           | $B_{11}$   | 4.794   | $B_{12}$             | 0.755    | $B_{44}$  | 1.416   |
| Soft mode-elastic | $B_{1xx}$  | -0.431  | $B_{1yy}$            | 0.033    | $B_{4yz}$ | -0.055  |
| Dipole            | $Z^*$      | 5.81    | $\varepsilon_\infty$ | 4.928    |           |         |

chemical analysis. The temperature dependence of the dielectric constant was measured at various frequencies in a temperature range from 5 K to 300 K using a Hewlett-Packard 4192A impedance analyzer and a cryostat with an estimated precision of 0.1 K. These measurements were performed on ceramic samples which were polished and cleaned, and sputtered gold electrodes were applied. Samples were annealed at 800 K and slowly cooled in order to eliminate strains caused by polishing. Powdered samples were used for the diffraction experiments. X-ray-diffraction measurements were performed on a high accuracy, two-axis diffractometer in a Bragg-Brentano geometry using Cu-K $\alpha$  wavelength issued from a 18-kW rotating anode generator, with diffraction angles precision better than 0.002 deg. The neutron powder diffraction patterns were collected at temperatures between 300 and 2 K on the 3T2 high resolution goniometer on a thermal source (1.227 Å) using the Orphe reactor facilities at Laboratoire Léon Brillouin (Saclay, France). Structural Rietveld refinements on both X-ray and neutron patterns were carried out with the XND software.

## B. THEORETICAL APPROACHES

In this study, two different (direct) first-principles codes, as well as a first-principles-derived technique, were used to obtain and/or extract various information. One of the two first-principles codes is denoted ABINIT<sup>18</sup>. We took advantage of its implementation of the linear response theory to compute the phonon dispersion curves of  $\text{BaZrO}_3$  at its low-temperature experimental lattice constant. Some technical details are as following. In this method we used Teter extended norm-conserving pseudopotentials<sup>19</sup> and the local-density approximation (LDA)<sup>20</sup>. The exchange-correlation functional was approximated using Perdew-Zunger parametrization<sup>21</sup> of Ceperley-Alder data<sup>22</sup>. The Ba 5s<sup>2</sup>, Ba 5p<sup>6</sup>, Ba 6s<sup>2</sup>, Zr 4s<sup>2</sup>, Zr 4p<sup>6</sup>, Zr 4d<sup>2</sup>, Zr 5s<sup>2</sup>, O 2s<sup>2</sup>, and O 2p<sup>6</sup> electrons are treated as valence electrons. A plane-wave cut off of 100 Ry was used to obtain convergence of the ground state total energy. Phonon frequencies were found to converge for dynamical matrices calculated on a 6×6×6 Monkhorst-Pack grid<sup>23</sup>.

The second first-principles code used in our study is de-

noted CUSP<sup>24</sup>. It also implements the LDA<sup>20</sup>, and the Ceperley-Alder exchange and correlation<sup>22</sup> as parameterized by Perdew and Zunger<sup>21</sup>. We also used the same valence electrons (indicated above) as in the ABINIT code. On the other hand, the pseudopotentials are those given by the Vanderbilt ultrasoft scheme<sup>25</sup>, and the plane-wave cutoff is chosen to be 25 Ry, which leads to converged results of physical properties of interest<sup>24</sup>. The CUSP code is used to calculate the energetics of  $\text{BaZrO}_3$  that are associated with the rotation of the oxygen octahedra, at its low-temperature experimental lattice constant. It is also used to derive, at this specific lattice constant, the 18 parameters of the first-principles-based effective Hamiltonian ( $H_{\text{eff}}$ ) approach developed in Ref. 26. These parameters are given in Table I.

We also perform simulations using such  $H_{\text{eff}}$  technique (and its parameters) to go beyond the abilities of direct first-principles techniques, namely to investigate *finite-temperature* properties of large  $\text{BaZrO}_3$  supercells. The degrees of freedom of this Hamiltonian are the so-called local modes (that are directly proportional to the spontaneous electrical polarization), and the strain variables (that characterize the crystallographic phase). The total energy,  $E_{\text{tot}}$  of  $H_{\text{eff}}$  contains five different interactions between local modes and/or strains, namely, a local-mode self energy, a long-range dipole-dipole interaction, a short-range interaction between local modes, an elastic energy and an interaction between local-modes and strain<sup>26</sup>. Monte-Carlo (MC) simulations are performed using  $E_{\text{tot}}$  in two different schemes: classical Monte Carlo (CMC)<sup>27</sup>, which neglects zero-point phonon vibrations and, path-integral quantum Monte Carlo (PI-QMC)<sup>28,29,30</sup>, which includes these quantum-mechanical zero-point motions. Consequently, comparison between the results of these two different Monte-Carlo techniques will allow the determination of quantum effects on structural and dielectric properties of  $\text{BaZrO}_3$ . 12×12×12 supercells (corresponding to 8,640 atoms) are used in all Monte-Carlo simulations. We typically perform 30,000 MC sweeps to thermalize the system and 70,000 more to compute averages, except at low temperatures in PI-QMC where more statistics is needed.

In PI-QMC, each 5-atom cell interacts with its images at neighboring imaginary times through a spring-like potential (representing the zero-point phonon vibrations as

implemented in PI-QMC formulations), while all the 5-atom cells interact with each other at the same imaginary time through the internal potential associated with  $E_{\text{tot}}$ . The product  $TP$ , where  $T$  is the simulated temperature and  $P$  is the number of imaginary time slices, controls the accuracy of the PI-QMC calculation<sup>31</sup>. In all our simulations we use  $TP=600$ , which we find leads to sufficiently converged results. Outputs of the PI-QMC simulations thus contain local-modes  $\mathbf{u}_i(t)$ , where  $i$  runs over the 5-atom unit cells of the studied supercell while the imaginary time  $t$  ranges between 1 and  $P$ . (Note that  $t = P = 1$  corresponds to CMC simulations.) Strain variables are another output of MC simulations.

### III. RESULTS

#### A. STRUCTURAL PROPERTIES

XRD and neutron scattering indicate that  $\text{BaZrO}_3$  is cubic (and thus paraelectric) down to 2 Kelvin (the minimal temperature accessed during our neutron scattering). Note that we are not aware of any previous measurement investigating the low-temperature, rather than high-temperature<sup>2,3,32</sup>, properties of  $\text{BaZrO}_3$ .

Our experimental result is consistent with the fact that we further find that our PI-QMC simulations using the effective Hamiltonian approach provide a vanishing supercell average of the local-modes down to 0 K and a resulting cubic ground-state. Interestingly, our CMC simulations also predict such paraelectric ground-state. This indicates that, unlike  $\text{KTaO}_3$ <sup>33,34</sup> and  $\text{SrTiO}_3$ <sup>16,29</sup> for which quantum effects suppress ferroelectricity in favor of paraelectricity, zero-point phonon vibrations do *not* affect the symmetry of the ground-state in  $\text{BaZrO}_3$ . On the other hand, Fig. 1 – which displays the predicted and measured temperature evolutions of the cubic lattice constant of  $\text{BaZrO}_3$  – clearly shows, via the comparison of CMC and PI-QMC results, how zero-point phonon vibrations *quantitatively* affect structural properties of  $\text{BaZrO}_3$ . Below 100 K, the zero-point phonon vibrations tend to prevent the lattice constant from decreasing when decreasing the temperature. Quantum effects thus increase the lattice constant with respect to classical predictions, with this increase becoming more pronounced as the temperature decreases. As a matter of fact, PI-QMC calculations result in (1) a dramatic change of thermal expansion below *versus* above 100 K, (2) a lattice constant that is nearly temperature-independent below  $\simeq 40$  K, and (3) a lattice parameter that is larger by  $10^{-3}$  Å from its CMC result at the lowest temperatures. Note that item (1) is clearly confirmed by our neutron scattering data (reported in Fig. 1 for 300, 100 and 2 K) that shows a relatively rapid  $\simeq 10^{-3}$  Å decrease of the lattice constant between 300 K and 100 K, while the difference in lattice parameters between 100 and 2 K is as small as  $3 \times 10^{-4}$  Å. Furthermore, items (1) and (2) have also previously been observed in the incipient  $\text{KTaO}_3$  system<sup>35</sup>

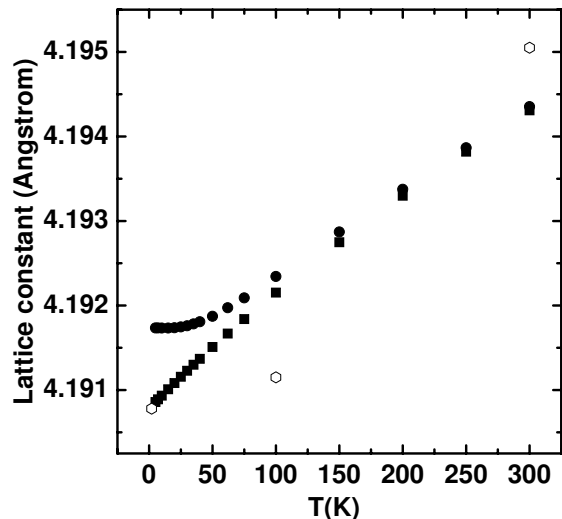


FIG. 1: Evolution of the cubic lattice constant as a function of temperature in  $\text{BaZrO}_3$ . Solid squares and solid circles correspond to the CMC and PI-QMC predictions, respectively, while the open symbols display the results of neutron scattering. Note that the CMC predictions exactly agree with the experimental data at low temperature as a consequence of our choice of the  $a_0$  parameter for the effective Hamiltonian approach (see Table I).

(but for different critical temperatures). Moreover, item (3) provides a measure of the (relatively small) quantitative effects of zero-point phonon vibrations on the lattice parameter *per se* (rather than on the thermal expansion) of  $\text{BaZrO}_3$ .

Fig. 1 also indicates that above 100 K, one can safely use the approximation that the cubic lattice parameter *linearly* depends on temperature with the thermal expansion coefficient being  $0.27 \times 10^{-5}$  (1/K),  $0.23 \times 10^{-5}$  (1/K) and  $0.47 \times 10^{-5}$  (1/K) for the CMC, PI-QMC and neutron scattering data, respectively. Our experimental value of  $0.47 \times 10^{-5}$  (1/K) compares rather well with the linear thermal expansion coefficient of  $0.69 \times 10^{-5}$  (1/K) previously measured by X-ray diffraction for temperature ranging between 273 and 873 K<sup>36</sup>. On the other hand, the thermal expansion of  $0.27 \times 10^{-5}$  (1/K) and  $0.23 \times 10^{-5}$  (1/K) predicted by our simulations underestimate the experimental values by a ratio of 2 – 3. This discrepancy between simulations and the measurements arises from the fact that the effective Hamiltonian approach only incorporates the ferroelectric-related vibrations among the optical modes, while an accurate description of thermal expansion requires to take into account *all* phonon modes<sup>37</sup>.

The effective Hamiltonian approach used in our study thus also neglects some phonon modes that may condense in  $\text{BaZrO}_3$ , such as the  $R_{25}$  modes that are associated with the rotation of the oxygen octahedra<sup>38</sup>. To check such possibility, we decided to compute the whole phonon dispersion of cubic  $\text{BaZrO}_3$ , using the lin-

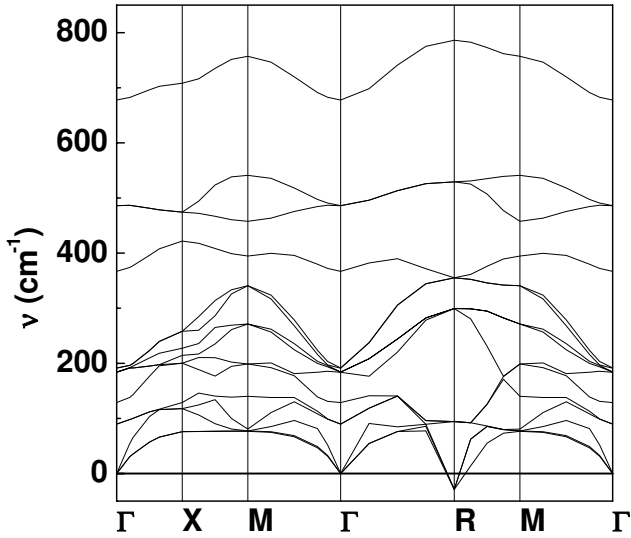


FIG. 2: Phonon dispersion of cubic  $\text{BaZrO}_3$ , from first principles calculations.

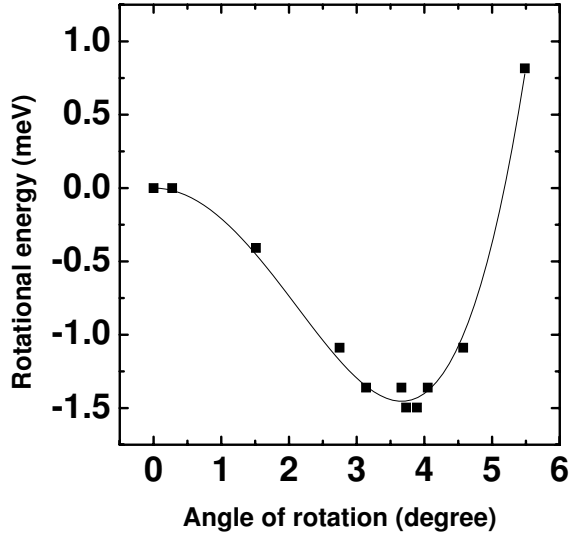


FIG. 3: Oxygen octahedra rotational energetics (per 5 atoms) versus the angle of the rotation about the  $[001]$  direction from first principles calculations. The zero energy correspond to the paraelectric state. Solid line is a guide for the eyes.

ear response theory as implemented in the first principles ABINIT code<sup>18</sup>. The results are shown in Fig. 2, and indeed confirm the previous *ab-initio* prediction<sup>38</sup> of the condensation of the R-point zone-boundary mode. (Note that these phonon calculations also confirm that  $\text{BaZrO}_3$  does not exhibit any ferroelectric instability at the  $\Gamma$  point, even when quantum statistics are neglected). One has to realize, though, that the instability associated with these antiferrodistortive motions is rather weak, as demonstrated by the relatively *small* negative value of the frequency. This is further evidenced in Fig. 3, that displays the total energy (as predicted by the first princi-

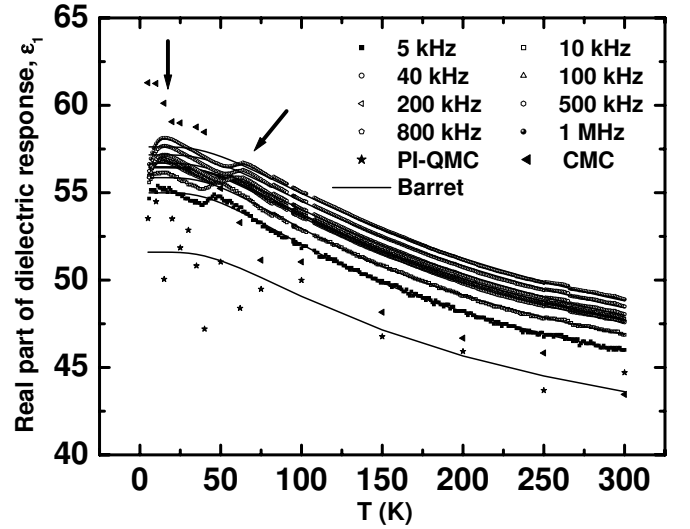


FIG. 4: Theoretical (using CMC and PI-QMC simulations) and experimental (for different frequencies) real part of the dielectric constant. Solid lines show the fit of the data into the Barret relation. The arrows indicate the position of the two observed dielectric anomalies that are discussed in the text

ples CUSP program<sup>24</sup>) versus the angle of the octahedra rotation about the  $[001]$  direction: the minimum energy (occurring for an angle about 4 deg) is only  $\simeq 1.5$  meV deeper than the energy of the paraelectric phase (associated with a zero angle). Such difference in energy corresponds to a rather small temperature of  $\approx 17$  K. It is thus highly possible that zero-point phonon vibrations prevent the occurrence (down to 2 K) of the macroscopic cubic paraelectric-to-antiferrodistortive phase transition, which would explain why our low-temperature XRD and neutron scattering experiments do not reveal any additional peak related to a doubling of the unit cell. This quantum-induced suppression may act either globally (i.e., different unit cells do exhibit some rotation of their oxygen octahedra, but these rotations are not long-range correlated) or locally (i.e., there is no rotation of the oxygen octahedra in any unit cell). We will come back to this point, and to this  $\approx 17$  K temperature, when discussing the results on dielectric properties.

## B. REAL PART OF THE DIELECTRIC RESPONSE

Fig. 4 shows our experimental determination of the real part of the dielectric response,  $\epsilon_1$ , versus temperature for different frequencies. The real part of the dielectric response of  $\text{BaZrO}_3$  increases as the temperature decreases from 300 K for any given frequency. It then exhibits an overall low-temperature saturation to a plateau having a value that is slightly dependent on the frequency (ranging between 55 and 58 for frequency varying be-

TABLE II: Coefficients of the fit of the real part of the dielectric response into the Barrett relation. All the parameters of all the fits are allowed to relax, except the parameters  $C$  and  $T_s$  for the fit of the PI-QMC data that are kept frozen to their deduced values from our experiments at the lowest frequency. Such freezing is necessary to allow the fit to converge because of the relatively large fluctuation inherent to PI-QMC simulations at low temperature.

| f[kHz]    | 5        | 10        | 40       | 100      | 200      | 500      | 800      | 1000     | PI-QMC    |
|-----------|----------|-----------|----------|----------|----------|----------|----------|----------|-----------|
| $C$       | 2900±185 | 2900 ±170 | 3200±200 | 3400±240 | 3600±280 | 4200±370 | 4600±440 | 4800±480 | 2900      |
| $T_s$ [K] | 81±2     | 80±2      | 80±2     | 80±2     | 80±2     | 77±3     | 76±3     | 75±3     | 81        |
| $T_0$ [K] | -99±10   | -102±9    | -114±10  | -124±12  | -135±13  | -160±17  | -175±19  | -182±20  | -114±21   |
| $B$       | 38.8±0.3 | 39.6±0.2  | 40.0±0.3 | 39.8±0.4 | 39.5±0.4 | 39.0±0.5 | 39.0±0.6 | 39.0±0.6 | 36.7± 1.4 |

tween 5 kHz and 1 MHz). The existence of such plateau has already been reported in the incipient ferroelectrics  $\text{KTaO}_3$ <sup>33,34</sup> and  $\text{SrTiO}_3$ <sup>16,29</sup>, and is usually thought to be associated with zero-point phonon vibrations. To check this fact, we also report in Fig. 4 the predictions from the  $H_{\text{eff}}$  approach using both CMC and PI-QMC techniques. It is obvious that using CMC, the real part of the dielectric response continuously increases to higher value when the temperature decreases while on the other hand the dielectric constant computed within PI-QMC tends to saturate, in overall, at low-temperature<sup>39</sup>. Our simulations thus prove that quantum fluctuations play an important role on the low-temperature dielectric responses of  $\text{BaZrO}_3$ , as in  $\text{KTaO}_3$ <sup>33,34</sup> and  $\text{SrTiO}_3$ <sup>16,29</sup>. However and as already mentioned in Section III.A, this quantum-induced modification of dielectricity in  $\text{BaZrO}_3$  is *not* accompanied by a suppression of ferroelectricity since  $\text{BaZrO}_3$  does not have any ferroelectric instability even in the classical regime – as indicated by the fact that our CMC simulations lead to a cubic paraelectric ground-state and a lack of peak in  $\epsilon_1$ . This distinguishes  $\text{BaZrO}_3$  from both  $\text{KTaO}_3$  and  $\text{SrTiO}_3$ . Figure 4 also reveals that our PI-QMC simulations yield predictions that are slightly smaller in magnitude than our experimental results. In fact, this has to be expected since (i) the measurements displayed in Fig. 4 demonstrate that decreasing frequency leads to a decrease of the dielectric response at any temperature and (ii) the calculations correspond to the static regime, *i.e.* to a zero frequency. We can thus conclude that the PI-QMC results are in overall quite accurate, especially when realizing that dielectric coefficients are related to the *derivative* of the polarization (*i.e.*, they are much more difficult to predict than properties that are directly proportional to polarization) and that the magnitude of  $\epsilon_1$  is rather small in  $\text{BaZrO}_3$  (e.g., the low-temperature plateau has a value that is smaller by  $\simeq 2$ -3 orders of magnitude than the corresponding ones in  $\text{KTaO}_3$ <sup>14,33,40</sup> and  $\text{SrTiO}_3$ <sup>16,41</sup>).

To further analyze our results, we fitted them using the Barret relation<sup>42</sup>

$$\epsilon_1 = \frac{C}{T_s \coth(\frac{T_s}{T}) - T_0} + B \quad (1)$$

where  $C$  and  $T_s$  are the so-called Curie constant and saturation temperature, respectively<sup>33,42,43</sup>.  $T_0$  is interpreted as being the classical Curie temperature (that

is, the Curie temperature if quantum effects would not exist) and  $B$  is a constant independent of temperature. The resulting fits are indicated by means of solid lines in Fig. 4, and the coefficients of these fits are given in Table II. In addition to the fact that the quality of these fits is in overall rather good (thus, confirming, as in  $\text{KTaO}_3$  and  $\text{SrTiO}_3$ , the relevance of the empirical Barret relation for describing quantum effects on dielectricity of perovskites), four features are particularly worth noticing related to these fits. First of all,  $T_0$  is (strongly) *negative* which confirms our theoretical findings that  $\text{BaZrO}_3$ , unlike  $\text{KTaO}_3$  and  $\text{SrTiO}_3$ , does *not* exhibit any ferroelectric instability even in the classical regime. Secondly, the  $T_s$  deduced from the experimental data is around 75-81 K, which is located in the temperature region for which PI-QMC predictions begin to significantly differ from CMC results for dielectric as well as structural properties (see Fig. 4 and Fig. 1). In other words, our simulations confirm the physical meaning usually associated with  $T_s$ , that is the temperature below which quantum effects play a non-negligible role on physical properties<sup>33,42,43</sup>. Thirdly, and also unlike in  $\text{KTaO}_3$ <sup>43</sup> and  $\text{SrTiO}_3$ <sup>41</sup>, the  $B$  parameter can *not* be neglected to get good fits in  $\text{BaZrO}_3$ . This latter difference is due to the fact that the low-temperature plateau is much larger in  $\text{KTaO}_3$  (around 4000)<sup>14,33,40</sup> and  $\text{SrTiO}_3$  (around 20,000)<sup>16,41</sup> than in  $\text{BaZrO}_3$  (around 55, see Fig. 4), or equivalently that  $T_0$  is positive in  $\text{KTaO}_3$ <sup>33,43</sup> and  $\text{SrTiO}_3$ <sup>41</sup> while being negative in  $\text{BaZrO}_3$ . Finally, two fine structures, existing in the experimental data, deviates from (and seem to be superimposed with respect to) the Barrett fit. More precisely, one hump appears in  $\epsilon_1$  around 50 K at the lowest used frequency *versus* 65 K for the highest frequency, while a second hump shows up around 15 K for (more-or-less) any frequency. The magnitude of this second hump decreases when decreasing frequency. Note that these relatively small humps do *not* appear within our CMC simulations, and that the large fluctuations inherent to the PI-QMC approach<sup>31</sup> do not allow us to assert if these humps are also predicted from our quantum simulations.

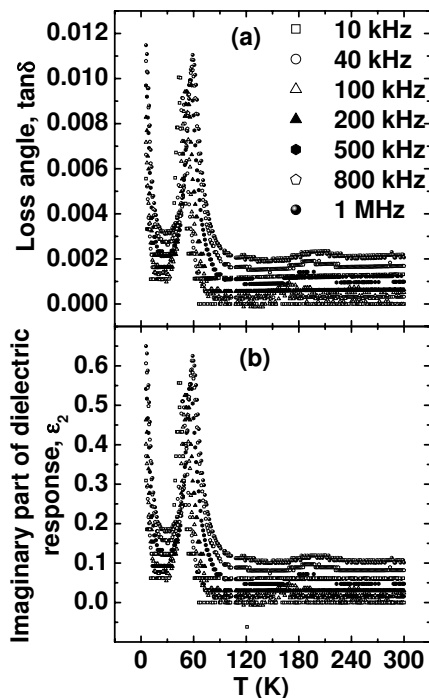


FIG. 5: Measured (a) loss angle,  $\tan\delta$ , and (b) imaginary part of the dielectric response,  $\epsilon_2$  at different frequencies *versus* temperature.

### C. IMAGINARY PART OF THE DIELECTRIC RESPONSE AND DIELECTRIC LOSS

Fig 5 displays the *imaginary* part of the dielectric response,  $\epsilon_2$  and the loss angle (as given by  $\tan\delta = \epsilon_2/\epsilon_1$ ) of BaZrO<sub>3</sub> versus temperature for frequencies ranging between 10 kHz and 1 MHz. All the results displayed in Fig 5 are from measurements since simulating loss on an *ab-initio* level is one of the most interesting and difficult challenges that remain to be accomplished nowadays. One can first notice from Fig 5 that both  $\epsilon_2$  and  $\tan\delta$  are very weak for the whole investigated frequency range, as also observed in Ba(Zn<sub>1/3</sub>Ta<sub>2/3</sub>)O<sub>3</sub>-BaZrO<sub>3</sub> solid solutions<sup>13</sup>. BaZrO<sub>3</sub> can thus be a material of choice to design high-Q compounds. Furthermore, our measurements show the existence of two loss anomalies, namely a peak in  $\epsilon_2$  (and  $\tan\delta$ ) around 50-65 K and a continuously increasing  $\epsilon_2$  (and  $\tan\delta$ ) when decreasing temperature below 25 K. These two anomalies are correlated with the humps seen in  $\epsilon_1$  since they occur at similar temperatures and since they behave in a similar fashion. For instance, both the peaks in  $\epsilon_1$  and  $\epsilon_2$ , occurring around 50 K at low frequency, shift to higher temperature when increasing the frequency. Similarly, the anomalies observed in  $\epsilon_1$  and  $\epsilon_2$  at very low temperature get more pronounced at higher frequency. Interestingly, the well-known Kramers-Kronig relations<sup>17</sup> imply that any peak/anomaly in  $\epsilon_1$  should be accompanied with a peak/anomaly in  $\epsilon_2$  (and vice-versa) at the same temperature. Such correlation

is thus indeed satisfied in BaZrO<sub>3</sub>, but surprisingly, does not seem to hold for pure SrTiO<sub>3</sub> and KTaO<sub>3</sub>. More precisely,  $\epsilon_2$  has been found to exhibit a peak in these two latter materials for a temperature around 30-50 K, but no corresponding peak has been seen in the real part of the dielectric response. One possible reason for this lack of observation in pure KTaO<sub>3</sub> and pure SrTiO<sub>3</sub> may be due to the fact that these two materials (unlike BaZrO<sub>3</sub>) have a *large* overall real part of the dielectric response<sup>16,33</sup> that “washes out” (i.e., prevents the observation of) weak superimposed peaks.

Furthermore, the dielectric anomalies seen in BaZrO<sub>3</sub> and reported in Figures 4 and 5 are also rather intriguing since our XRD and neutron scattering do not detect any structural phase transition down to 2 K. A discussion about their possible causes is given in the next section.

## IV. DISCUSSIONS

We believe that the enhancement in the real and imaginary parts of the dielectric responses occurring at temperature around  $\simeq 15$  K is due to the activation of the oxygen octahedra rotation in BaZrO<sub>3</sub>. This belief is based on the fact that the minimum energy associated with antiferrodistortive motions is predicted to correspond to a temperature that is very close to the one at which these enhancements begin to occur, namely 17 K (see Fig. 3 and Sec. III A). The zero-point phonon vibrations may annihilate the *long-range order* of such rotation down to 2 K, which would explain our X-ray diffraction and neutron scattering results. However, these quantum-induced effects likely can not prevent the octahedra rotation from occurring at a *local* scale (especially at very low temperature), which would be consistent with the fact that  $\epsilon_2$  increases when decreasing the temperature below 25 K (see Fig 5).

Regarding the unusual dielectric features occurring around 50 K, it is important to realize that a frequency-dependent peak has previously been reported for  $\tan\delta$  and  $\epsilon_2$  in several other perovskite systems (e.g., BaTiO<sub>3</sub>:La, SrTiO<sub>3</sub>:La, SrTiO<sub>3</sub>, SrTiO<sub>3</sub>:Ca, K(Ta,Nb)O<sub>3</sub>, (Pb,Lu)TiO<sub>3</sub>:Cu, KTaO<sub>3</sub>) *near a similar temperature* (see, e.g. Refs 14,15,16,34 and references therein). For instance,  $\epsilon_2$  peaks around 40 K for low frequency in KTaO<sub>3</sub><sup>14,34</sup>. It is commonly believed that the reasons behind these peaks is the existence of unavoidable impurity ions having a different valence than the host atoms (see Refs. 44,45 and reference therein). In such a case, these peaks should become more pronounced when intentionally doping the sample with impurities, as consistent with the fact that adding up to 3% of Mn<sup>2+</sup> in KTaO<sub>3</sub> leads to a noticeable peak in the real part of the dielectric response around 40 K<sup>44</sup>. Observing and understanding the effects of doping on physical properties of BaZrO<sub>3</sub> is thus of importance to confirm this (general) possibility, but goes beyond the scope of the present article. One particular previous study<sup>15</sup> further stipu-

lates that it is a polaronic relaxation – that is, a coupling between the free charge carriers arising from the impurity ions and the lattice properties of the host material – that causes such weak dielectric anomalies. As done in Ref. 15, such possibility can be checked by extracting the temperature-dependency and frequency-dependency of relaxation time via an analysis of loss dynamics using, e.g., Cole-Cole formula loss<sup>17</sup>. Such analysis, to be accurate, requires the investigation of  $\varepsilon_1$  and  $\varepsilon_2$  under a range of frequency that is much wider than the one available for the present study.

## V. CONCLUSIONS

In summary, we combined measurements with first-principles-based techniques to investigate the low-temperature properties of BaZrO<sub>3</sub>. This system is found to be cubic and macroscopically paraelectric down to 2 K. Unlike the “better-studied” KTaO<sub>3</sub><sup>33,40</sup> and SrTiO<sub>3</sub><sup>16,29</sup> incipient ferroelectrics, the zero-point phonon vibrations do *not* suppress ferroelectricity in BaZrO<sub>3</sub>. In other words, this latter material is also paraelectric in the classical regime. On the other hand, quantum effects lead to the saturation of the cubic lattice parameter below  $\simeq$  40 K.

Despite having no long-range-order structural phase transition, BaZrO<sub>3</sub> exhibits the following striking dielectric features: (1) the  $\varepsilon_1$  real part of the dielectric response saturates in overall at low temperature (namely, below  $\simeq$  40 K) to a value  $\simeq$  55. Our PI-QMC simulations are in rather good agreement with experimental data, and show that such saturation is caused by zero-point phonon vibrations; (2) the temperature behavior of  $\varepsilon_1$  can be well fitted by the empirical Barrett relation when allowing the  $B$  parameter to differ from zero in this fit; (3) two peaks or fine structures are observed in  $\varepsilon_1$  around 50-65 K and 15 K, respectively. The first peak shifts to lower temperatures when decreasing the frequency, while the second one occurs at around the same temperature but decreases in magnitude when decreasing the frequency; (4)

these two fine structures are associated with anomalies in the imaginary part of the dielectric response,  $\varepsilon_2$ , which peaks at around 50-65 K while suddenly and continuously increases when decreasing temperature below 15 K.

By comparing with previously reported data in other perovskites and adopting some related interpretations, we propose that the highest-temperature dielectric anomalies are caused by defects like oxygen vacancies and/or unavoidable impurity ions such as Fe<sup>3+</sup> — which, e.g., are the source of free charge carriers, that can interact with a soft lattice to create a polaronic state responsible for the dielectric anomaly<sup>15</sup>. Furthermore, our (direct) first-principles calculations suggest that the lowest-temperature dielectric anomalies may result from local rotation of the oxygen octahedra.

In order to acquire a deeper knowledge of perovskites, it is interesting to compare items (1-4) with corresponding features in KTaO<sub>3</sub> and SrTiO<sub>3</sub>. For instance,  $\varepsilon_1$  also saturates at low temperature in KTaO<sub>3</sub> and SrTiO<sub>3</sub>, but with a much higher value of the plateau (as a result of the quantum-induced *suppression* of ferroelectricity in these latter compounds). Such high value of the plateau explains why the  $B$  coefficient is generally omitted in the Barrett fit of KTaO<sub>3</sub> and SrTiO<sub>3</sub>. It is also highly plausible, as we believe it, that such high  $\varepsilon_1$  prevents the observation of the hump that should be associated (according to the Kramers-Kronig relation<sup>17</sup>) with the peak of  $\varepsilon_2$  seen around 30-50 K in KTaO<sub>3</sub><sup>14,15</sup> and SrTiO<sub>3</sub><sup>15,16</sup>.

We hope that our work stimulates further investigations aimed at checking our suggestions, in particular, and understanding dielectric anomalies in perovskites, in general.

## ACKNOWLEDGMENTS

The authors would like to thank Jorge Íñiguez and David Vanderbilt for providing the code for PI-QMC simulations. This work is supported by ONR grants N 00014-01-1-0365 (CPD), N00014-97-1-0048, N00014-04-1-0413 and 00014-01-1-0600, by NSF grants DMR-0404335 and DMR-9983678 and by DOE grant DE-FG02-05ER46188.

<sup>1</sup> P. S. Dobal, A. Dixit, R. S. Katiyar, Z. Yu, R. Guo and A. S. Bhalla, J. Appl. Phys. **89**, 8085 (2001).

<sup>2</sup> Abdul-Majeed Azad and S. Subramaniam, Materials Research Bulletin **37**, 85 (2002); Materials Research Bulletin **37**, 11 (2002).

<sup>3</sup> Abdul-Majeed Azad, S. Subramaniam and T. W. Dung, Journal of Alloys and compounds **334**, 118 (2002).

<sup>4</sup> B. Robertz, F. Boschini, R. Cloots and A. Rulmont, International Journal of Inorganic Materials **3**, 1185 (2001).

<sup>5</sup> N. Lecerf, S. Mathur, H. Shen, M. Veith and S. Hüfner, Scripta Mater. **44**, 2157 (2001).

<sup>6</sup> G. Taglieri, M. Tersigni, P. L. Villa and C. Mondelli, International Journal of Inorganic Materials **1**, 103 (1999).

<sup>7</sup> E. Celik, Y. Akin, I. H. Mutlu, W. Sigmund and Y. S.

Hascicek, Physica C **382**, 355 (2002).

<sup>8</sup> M. Koopman, S. Duncan, K. K. Chawla and C. Coffin, Composites: part A **32** 1039 (2001).

<sup>9</sup> J. Brzezińska-Miecznik, K. Haberko and M. M. Bucko, Materials Letters **56**, 273 (2002).

<sup>10</sup> L. Chai, M. A. Akbas, P. K. Davies and J. B. Parise, Materials Research Bulletin **32**, 1261 (1997).

<sup>11</sup> A. Erb, E. Walker and R. Flükiger, Physica C **245**, 245 (1995).

<sup>12</sup> K. Tanaka, K. Suzuki, D. Fu, K. Nishizawa, T. Miki and K. Kato, Key Engineering Materials **269**, 57 (2004).

<sup>13</sup> P. K. Davies, in *Proceedings of the Symposium on Materials and Preprocessing for Wireless Communications* ed. T. Negas, J. Am. Ceram. Soc. **53** 137, (1994).

- <sup>14</sup> B. Salce, J. L. Grail and L. A. Boatner, J. Phys: Condens. Matter **6**, 4077 (1994).
- <sup>15</sup> O. Bidault, M. Maglione, M. Actis, M. Kchikech, and B. Salce, Phys. Rev. B **52**, 4191 (1995).
- <sup>16</sup> R. Viana, P. Lunkenheimer, J. Hemberger, R. Böhmer, and A. Loidl, Phys. Rev. B **50**, 601(R) (1994).
- <sup>17</sup> B. K. P. Scaife, Principles of Dielectrics, Clarendon Press, Oxford (1989).
- <sup>18</sup> The ABINIT code is a common project of the Universite Catholique de Louvain, Corning, InC., and other contributors (URL <http://www.abinit.org>)
- <sup>19</sup> M. Teter, Phys. Rev. B **48**, 5031 (1993).
- <sup>20</sup> P. Hohenberg and W. Kohn, Phys. Rev. **136**, B864 (1964); W. Kohn and L.J. Sham, *ibid.* **140**, A1133 (1965).
- <sup>21</sup> J. Perdew and A. Zunger, Phys. Rev. B **23**, 5048 (1981);
- <sup>22</sup> D.M. Ceperley and B.J. Alder, Phys. Rev. Lett. **45**, 566 (1980).
- <sup>23</sup> H.J. Monkhorst and J.D. Pack, Phys. Rev. B **13**, 5188 (1976).
- <sup>24</sup> R.D. King-Smith and D. Vanderbilt, Phys. Rev. B **47**, 1651 (1993).
- <sup>25</sup> D. Vanderbilt, Phys. Rev. B **41**, 7892 (1990).
- <sup>26</sup> W. Zhong, D. Vanderbilt and K. M. Rabe, Phys. Rev. Lett. **73**, 1861 (1994); *Phys. Rev. B* **52**, 6301 (1995).
- <sup>27</sup> N. Metropolis, A. W. Rosenbluth, M. N. Rosenbluth, A. H. Teller and E. Teller, J. Chem. Phys. **21**, 1087 (1953).
- <sup>28</sup> J. Íñiguez and D. Vanderbilt, Phys. Rev. Lett. **89**, 115503-1 (2002).
- <sup>29</sup> W. Zhong and David Vanderbilt, Phys. Rev. B **53**, 5047 (1996).
- <sup>30</sup> D. M. Ceperley, Rev. Mod. Phys. **67**, 279 (1995).
- <sup>31</sup> A. Cuccoli, A. Macchi, G. Pedrolli, V. Tognetti, and R. Vaia, Phys. Rev. B **51**, 12369 (1995).
- <sup>32</sup> V. M. Fuenzalida and M. E. Pilleux, J. Mater. Res., **10**, 2749 (1996)
- <sup>33</sup> A. R. Akbarzadeh, L. Bellaiche, K. Leung, J. Íñiguez and David Vanderbilt, Phys. Rev. B **70**, 054103 (2004).
- <sup>34</sup> G. A. Samara, J. Phys. Condens. Matter **15**, R367 (2003).
- <sup>35</sup> G. Samara, and B. Morosin, Phys. Rev. B **8**, 1256 (1973).
- <sup>36</sup> Y. Zhao and D. J. Weidner, Phys. Chem. Mineral, **18**, 294 (1991).
- <sup>37</sup> S. Tinte, J. Íñiguez, K. M. Rabe and D. Vanderbilt, Phys. Rev. B **67**, 064106 (2003).
- <sup>38</sup> W. Zhong and David Vanderbilt, Phys. Rev. Lett. **74**, 2587 (1995).
- <sup>39</sup> Dielectric constants at different temperatures are typically calculated using the correlation function method. However, for some temperatures and in order to get better statistics and smoother curves, we also used the difference between polarization under different electric field to extract the dielectric constant. These two kinds of methods provide similar results. For instance, in PI-QMC at T=75 K correlation function yield a value of 48.75 for dielectric constant while on the other hand finite difference method lead to 49.48 when the electric field along either of x, y or z directions is gradually increased from zero to  $5 \times 10^6$  V/m.
- <sup>40</sup> G. Samara, in *Solid State Physics*, ed. H. Ehrenreich and F. Spaepen, Academic Press **56**, 239 (2001).
- <sup>41</sup> J. Dec and W. Kleemann, Solid State Commun. **106**, 695 (1998).
- <sup>42</sup> J. H. Barrett, Phys. Rev. **86**, 118 (1952).
- <sup>43</sup> C. Ang, A.S. Bhalla and L.E. Cross, Phys. Rev. B **64**, 184104 (2001).
- <sup>44</sup> G. A. Samara and, L. Venturini, in *First-Principles Calculations for Ferroelectrics: Fifth Williamsburg Workshop*, R. E. Cohen, and P. Gehring ed. (IOP, Journal of Physics: Condensed Matter, 2004),p. 122.
- <sup>45</sup> V. V. Laguta, M. D. Glinchuk, I. P. Bykov, J. Rosa, L. Jastrabík, M. Savinov and, Z. Trybula, Phys. Rev. B **61**, 3897 (2000).